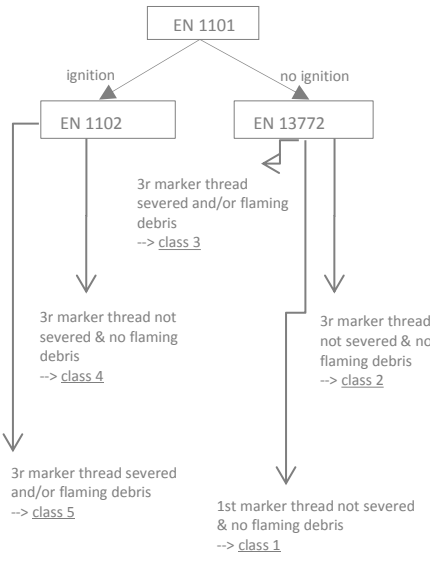


Document number:	<u>12-0509-EN</u>	Report date:	<u>13/06/2012</u>
Fabric reference:	<u>Blockbuster</u> <u>(beige)</u>	Date analyses:	<u>11/6/12 - 13/6/12</u>
Customer:	<u>BRU Textiles</u> <u>Satenrozen 2A</u> <u>B-2550 Kontich</u>	Place analyses:	<u>Labotex</u>
		Date of request:	<u>29/02/2012</u>
		Samples received	<u>28/02/2012</u>

Testing and conditioning in standard atmosphere, T (20+/-2)°C and RH (65+/-4)%

(This report has been fully revised because the new version of EN13772)

Specification	Results	Remarks	!																																																																										
<p><b>Burning behaviour of fabrics for curtains &amp; drapes</b></p> <p>EN 13773</p> <p>conditioning min. 24h in standard atmosphere</p> <p>used gas: propane flame height: 40mm bottom edge ignition</p> <p><u>flow chart EN 13773</u></p> 	<p>a) <u>EN 1101</u></p> <p>Test EN1101 is performed after subjecting the fabric to 1 washing cycle, based on the recommended washing instruction.</p> <table border="1"> <thead> <tr> <th>flame application time</th> <th>warp</th> <th>weft</th> </tr> </thead> <tbody> <tr><td>1s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>2s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>3s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>4s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>5s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>10s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>15s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> </tbody> </table> <p>Mean ignition time warp: <u>NA</u></p> <p>Mean ignition time weft: <u>NA</u></p> <p>Minimum ignition time: <u>NA</u></p> <p>b) <u>EN 13772 before washing</u></p> <table border="1"> <thead> <tr> <th>warp</th> <th>face</th> <th>reverse</th> <th>reverse</th> <th>reverse</th> </tr> </thead> <tbody> <tr><td>1st marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>2nd marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>3rd marker thread severed</td><td></td><td></td><td></td><td></td></tr> <tr><td>time to severance 3rd marker thread (s)</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>destroyed length (mm)</td><td>98</td><td>109</td><td>99</td><td>98</td></tr> <tr><td>flaming debris</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> </tbody> </table>	flame application time	warp	weft	1s	no ignition	no ignition	2s	no ignition	no ignition	3s	no ignition	no ignition	4s	no ignition	no ignition	5s	no ignition	no ignition	10s	no ignition	no ignition	15s	no ignition	no ignition	20s	no ignition	no ignition	20s	no ignition	no ignition	20s	no ignition	no ignition	20s	no ignition	no ignition	20s	no ignition	no ignition	warp	face	reverse	reverse	reverse	1st marker thread severed	no	no	no	no	2nd marker thread severed	no	no	no	no	3rd marker thread severed					time to severance 3rd marker thread (s)	no	no	no	no	destroyed length (mm)	98	109	99	98	flaming debris	no	no	no	no		<input type="checkbox"/>
flame application time	warp	weft																																																																											
1s	no ignition	no ignition																																																																											
2s	no ignition	no ignition																																																																											
3s	no ignition	no ignition																																																																											
4s	no ignition	no ignition																																																																											
5s	no ignition	no ignition																																																																											
10s	no ignition	no ignition																																																																											
15s	no ignition	no ignition																																																																											
20s	no ignition	no ignition																																																																											
20s	no ignition	no ignition																																																																											
20s	no ignition	no ignition																																																																											
20s	no ignition	no ignition																																																																											
20s	no ignition	no ignition																																																																											
warp	face	reverse	reverse	reverse																																																																									
1st marker thread severed	no	no	no	no																																																																									
2nd marker thread severed	no	no	no	no																																																																									
3rd marker thread severed																																																																													
time to severance 3rd marker thread (s)	no	no	no	no																																																																									
destroyed length (mm)	98	109	99	98																																																																									
flaming debris	no	no	no	no																																																																									

Document number:	<u>12-0509-EN</u>	Report date:	<u>13/06/2012</u>
Fabric reference:	<u>Blockbuster</u> <u>(beige)</u>	Date analyses:	<u>11/6/12 - 13/6/12</u>
Customer:	<u>BRU Textiles</u> <u>Satenrozen 2A</u> <u>B-2550 Kontich</u>	Place analyses:	<u>Labotex</u>
		Date of request:	<u>29/02/2012</u>
		Samples received	<u>28/02/2012</u>


Testing and conditioning in standard atmosphere, T (20+/-2)°C and RH (65+/-4)%

(This report has been fully revised because the new version of EN13772)

Specification	Results					Remarks	!
	weft	face	reverse	reverse	reverse		
1st marker thread severed	no	no	no	no	no		
2nd marker thread severed	no	no	no	no	no		
3rd marker thread severed							
time to severance 3rd marker thread (s)	no	no	no	no	no		
destroyed length (mm)	93	106	97	101			
flaming debris	no	no	no	no	no		
c) <u>classification</u>							
	class 1	x					
	class 2	_____					
	class 3	_____					
	class 4	_____					



Labotex certifies that the results mentioned in this report are obtained after testing in accordance with the procedure and equipment specified by the concerned standards, unless noted differently.



Elke Dierck - Technical Manager

The results in this report only relate to the tested items.

Samples will be returned to the customer with the certificate, if possible. Samples will not be retained, unless specified by the customer. Retained samples will be kept for maximum one year unless a specific retention period is necessary.

This report can not be copied unless in its complete form and with written approval of Labotex.