

Document number: 16-0620-EN

Fabric reference: Jaime
(brown)

Customer: BRU Textiles
Satenrozen ZA
B-2550 Kontich

Report date: 5/10/2016

Date analyses: 27/04/2016-02/05/2016

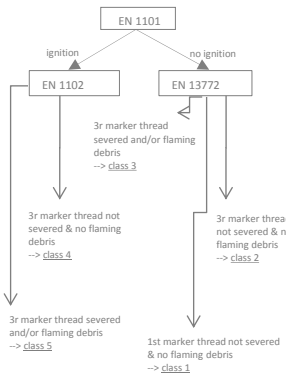
Place analyses: Labotex

Date of request: 21/04/2016

Samples received: 21/04/2016

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

(SC as TM)

Specification	Results	Remarks	!																																																																																																	
<p>Burning behaviour of fabrics for curtains & drapes</p> <p>EN 13773</p> <p>conditioning min. 24h in standard atmosphere</p> <p>used gas: propane</p> <p>flame height: 40mm</p> <p>bottom edge ignition</p> <p>size EN1101: 200x80mm</p> <p>size EN13772: 560x170mm</p> <p>flow chart EN 13773</p> 	<p>a) <u>EN 1101</u></p> <p>Test EN1101 is performed after subjecting the fabric to 1 washing cycle, based on the recommended washing instruction.</p> <table border="1"> <thead> <tr> <th>flame application time</th> <th>warp</th> <th>weft</th> </tr> </thead> <tbody> <tr><td>1s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>2s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>3s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>4s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>5s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>10s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>15s</td><td>no ignition</td><td>no ignition</td></tr> <tr><td>20s</td><td>no ignition</td><td>no ignition</td></tr> </tbody> </table> <p>Mean ignition time warp: <u>NA</u></p> <p>Mean ignition time weft: <u>NA</u></p> <p>Minimum ignition time: <u>NA</u></p> <p>b) <u>EN 13772 before washing</u></p> <table border="1"> <thead> <tr> <th>warp</th> <th>face</th> <th>reverse</th> <th>reverse</th> <th>reverse</th> </tr> </thead> <tbody> <tr><td>1st marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>2nd marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>3rd marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>time to severance 3rd marker thread (s)</td><td>0</td><td>0</td><td>0</td><td>0</td></tr> <tr><td>destroyed length (mm)</td><td>130</td><td>142</td><td>138</td><td>120</td></tr> <tr><td>flaming debris</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> </tbody> </table> <table border="1"> <thead> <tr> <th>weft</th> <th>face</th> <th>reverse</th> <th>reverse</th> <th>reverse</th> </tr> </thead> <tbody> <tr><td>1st marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>2nd marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>3rd marker thread severed</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> <tr><td>time to severance 3rd marker thread (s)</td><td>0</td><td>0</td><td>0</td><td>0</td></tr> <tr><td>destroyed length (mm)</td><td>117</td><td>132</td><td>135</td><td>135</td></tr> <tr><td>flaming debris</td><td>no</td><td>no</td><td>no</td><td>no</td></tr> </tbody> </table>	flame application time	warp	weft	1s	no ignition	no ignition	2s	no ignition	no ignition	3s	no ignition	no ignition	4s	no ignition	no ignition	5s	no ignition	no ignition	10s	no ignition	no ignition	15s	no ignition	no ignition	20s	no ignition	no ignition	warp	face	reverse	reverse	reverse	1st marker thread severed	no	no	no	no	2nd marker thread severed	no	no	no	no	3rd marker thread severed	no	no	no	no	time to severance 3rd marker thread (s)	0	0	0	0	destroyed length (mm)	130	142	138	120	flaming debris	no	no	no	no	weft	face	reverse	reverse	reverse	1st marker thread severed	no	no	no	no	2nd marker thread severed	no	no	no	no	3rd marker thread severed	no	no	no	no	time to severance 3rd marker thread (s)	0	0	0	0	destroyed length (mm)	117	132	135	135	flaming debris	no	no	no	no		<input type="checkbox"/>
flame application time	warp	weft																																																																																																		
1s	no ignition	no ignition																																																																																																		
2s	no ignition	no ignition																																																																																																		
3s	no ignition	no ignition																																																																																																		
4s	no ignition	no ignition																																																																																																		
5s	no ignition	no ignition																																																																																																		
10s	no ignition	no ignition																																																																																																		
15s	no ignition	no ignition																																																																																																		
20s	no ignition	no ignition																																																																																																		
warp	face	reverse	reverse	reverse																																																																																																
1st marker thread severed	no	no	no	no																																																																																																
2nd marker thread severed	no	no	no	no																																																																																																
3rd marker thread severed	no	no	no	no																																																																																																
time to severance 3rd marker thread (s)	0	0	0	0																																																																																																
destroyed length (mm)	130	142	138	120																																																																																																
flaming debris	no	no	no	no																																																																																																
weft	face	reverse	reverse	reverse																																																																																																
1st marker thread severed	no	no	no	no																																																																																																
2nd marker thread severed	no	no	no	no																																																																																																
3rd marker thread severed	no	no	no	no																																																																																																
time to severance 3rd marker thread (s)	0	0	0	0																																																																																																
destroyed length (mm)	117	132	135	135																																																																																																
flaming debris	no	no	no	no																																																																																																

Document number: 16-0620-EN

Fabric reference: Jaime
(brown)

Customer: BRU Textiles
Satenrozen ZA
B-2550 Kontich

Report date: 5/10/2016

Date analyses: 27/04/2016-02/05/2016

Place analyses: Labotex

Date of request: 21/04/2016

Samples received: 21/04/2016

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

(SC as TM)

Specification	Results	Remarks	!																																																																														
	<p>c) <u>EN 13772 after washing</u></p> <p><i>This washing procedure consists of 12 cycles according to standard ISO6330.</i></p> <table border="1"> <thead> <tr> <th>warp</th> <th>face</th> <th>reverse</th> <th>reverse</th> <th>reverse</th> </tr> </thead> <tbody> <tr> <td>1st marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>2nd marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>3rd marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>time to severance 3rd marker thread (s)</td> <td>0</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>destroyed length (mm)</td> <td>127</td> <td>130</td> <td>152</td> <td>117</td> </tr> <tr> <td>flaming debris</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> </tbody> </table> <table border="1"> <thead> <tr> <th>weft</th> <th>face</th> <th>reverse</th> <th>reverse</th> <th>reverse</th> </tr> </thead> <tbody> <tr> <td>1st marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>2nd marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>3rd marker thread severed</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> <tr> <td>time to severance 3rd marker thread (s)</td> <td>0</td> <td>0</td> <td>0</td> <td>0</td> </tr> <tr> <td>destroyed length (mm)</td> <td>118</td> <td>128</td> <td>110</td> <td>127</td> </tr> <tr> <td>flaming debris</td> <td>no</td> <td>no</td> <td>no</td> <td>no</td> </tr> </tbody> </table> <p>c) <u>classification</u></p> <table> <tr> <td>class 1</td> <td><u> x </u></td> </tr> <tr> <td>class 2</td> <td><u> </u></td> </tr> <tr> <td>class 3</td> <td><u> </u></td> </tr> <tr> <td>class 4 or 5</td> <td><u> </u></td> </tr> </table>	warp	face	reverse	reverse	reverse	1st marker thread severed	no	no	no	no	2nd marker thread severed	no	no	no	no	3rd marker thread severed	no	no	no	no	time to severance 3rd marker thread (s)	0	0	0	0	destroyed length (mm)	127	130	152	117	flaming debris	no	no	no	no	weft	face	reverse	reverse	reverse	1st marker thread severed	no	no	no	no	2nd marker thread severed	no	no	no	no	3rd marker thread severed	no	no	no	no	time to severance 3rd marker thread (s)	0	0	0	0	destroyed length (mm)	118	128	110	127	flaming debris	no	no	no	no	class 1	<u> x </u>	class 2	<u> </u>	class 3	<u> </u>	class 4 or 5	<u> </u>		
warp	face	reverse	reverse	reverse																																																																													
1st marker thread severed	no	no	no	no																																																																													
2nd marker thread severed	no	no	no	no																																																																													
3rd marker thread severed	no	no	no	no																																																																													
time to severance 3rd marker thread (s)	0	0	0	0																																																																													
destroyed length (mm)	127	130	152	117																																																																													
flaming debris	no	no	no	no																																																																													
weft	face	reverse	reverse	reverse																																																																													
1st marker thread severed	no	no	no	no																																																																													
2nd marker thread severed	no	no	no	no																																																																													
3rd marker thread severed	no	no	no	no																																																																													
time to severance 3rd marker thread (s)	0	0	0	0																																																																													
destroyed length (mm)	118	128	110	127																																																																													
flaming debris	no	no	no	no																																																																													
class 1	<u> x </u>																																																																																
class 2	<u> </u>																																																																																
class 3	<u> </u>																																																																																
class 4 or 5	<u> </u>																																																																																



Labotex certifies that the results mentioned in this report are obtained after testing in accordance with the procedure and equipment specified by the concerned standards, unless noted differently.



Joeri Neys - Laboratory Manager

Labotex has the competence to perform tests in accordance with the requirements of standard NBN EN ISO/IEC 17025. The scope of this accreditation can be obtained on request.

The results in this report only relate to the tested items.

Samples will be returned to the customer with the certificate, if possible. Samples will not be retained, unless specified by the customer. Retained samples will be kept for maximum one year unless a specific retention period is necessary.

This report can not be copied unless in its complete form and with written approval of Labotex (Kontich).

Sampling is performed by the customer. Fabric analysed as received